

## Full Length Research Paper

# Green synthesis of silver monometallic and copper-silver bimetallic nanoparticles using *Kigelia africana* fruit extract and evaluation of their antimicrobial activities

Providence B. Ashishie<sup>1</sup>, Chinyere A. Anyama<sup>1</sup>, Ayi A. Ayi<sup>1\*</sup>, Charles O. Oseghale<sup>2</sup>, Elijah T. Adesuji<sup>2</sup> and Ayomide H. Labulo<sup>2</sup>

<sup>1</sup>Department of Pure and Applied Chemistry, University of Calabar, P. M. B.1115-Calabar, 542002, Nigeria.

<sup>2</sup>Department of Chemistry, Federal University Lafia, Nasarawa State, Nigeria.

Received 20 September, 2017; Accepted 31 October, 2017

Aqueous extract of *Kigelia africana* fruits have been utilized in the syntheses of silver nanoparticles (AgNPs) and copper-silver bimetallic nanoparticles (Ag-CuNPs). The synthesized nanoparticles have been characterized using UV-vis, Fourier-transform infrared spectroscopy (FTIR), scanning electron microscopy/energy dispersive X-ray analysis (SEM/EDX), x-ray diffraction (XRD) and transmission electron microscopy (TEM). The antimicrobial activities have been evaluated against both Grams-negative and Grams-positive strains of bacteria and fungus. The UV-vis and FTIR techniques revealed the formation of nanoparticles and the active components were adsorbed on the surface of the particles thereby stabilizing the nanoparticles. The SEM reveals uniform microspheres of AgNPs and anisotropic particles for AgCuNPs. TEM shows a particle size of 10 nm. The nanoparticles inhibit the growth of both Grams-negative and Grams-positive bacteria. The present nanoparticles synthesized from aqueous extract of *K. africana* fruits inhibits *Klebsiella pneumoniae* more than any of the antibiotics tested in this study. It competes very well with augmentin against *Pseudomonas aeruginosa* and with meropenem against *Candida albicans* with inhibition zones of 23 and 25 mm, respectively. The bimetallic nanoparticles have demonstrated effectiveness against *Staphylococcus aureus*, with maximum inhibition zone of 27 mm.

**Key words:** Green synthesis, bioreduction, nanoparticles, bimetallic particles, *Kigelia africana*, antimicrobial activities.

## INTRODUCTION

The synthesis of metal and/or bimetallic nanoparticles is a growing field of interest with various inputs from diverse disciplines. This has formed the bedrock for implementation of novel technologies. The intense

research interest is due to diverse applications in different fields, for example, biomedical (Chaloupka et al., 2010), drug delivery (Prow et al., 2011), water treatment (Dankovich and Gray, 2011), agriculture (Nair et al., 2010)

and sensors (Pandey et al., 2012; Pandey et al., 2013a, b; Tran et al., 2013). Furthermore, the larvicidal, antibacterial, antifungal anticoagulant and thrombolytic activities of silver nanoparticles have been extensively investigated (Lateef et al., 2015, 2016a; Lateef et al., 2016c). Consequently, a number of studies are geared towards development of suitable protocols for the rational synthesis of metal and/or bimetallic nanoparticles in an eco-friendly approach. A number of physio-chemical techniques involving chemical reduction (Park et al., 2008; Ayi et al., 2010, 2015; Khan et al., 2011a), gamma ray radiation (Chen et al., 2007), micro emulsion (Zhang et al., 2006), electrochemical method (Reicha et al., 2012), laser ablation (Abid et al., 2002), autoclave (Yang and Pan, 2012), microwave (Khan et al., 2011b) and photochemical reduction (Alarcon et al., 2012) are commonly employed in the synthesis of metal and/or bimetallic nanoparticles. Although these methods have been quite effective, the risks associated with the use of toxic chemicals as well as high operational cost and energy requirement have limited their use.

Recently, different research groups have reported on the use of green synthesis as an environmentally benign in the preparation of silver nanoparticles. This involves the use of extracts of different parts of plant (Sathishkumar et al., 2009; Tripathi et al., 2009; Prathna et al., 2011; Sivarraman et al., 2009). Mubayi et al. (2012) and Vijaykumar et al. (2014), reported on the use of extract of *Moringa oleifera* and *Boerhaavia diffusa*, respectively, to prepare silver nanoparticles. The biogenic synthesis of silver nanoparticles have been reported recently using a pod extract of *Cola nitida* (Lateef et al., 2015, 2016b), cell-free extract of *Bacillus safensis* (Lateef et al., 2016c) as well as the use of agro-wastes, enzymes and pigments (Adelere and Lateef, 2016). The important plants that have been used to date, include amongst others, the following: *Tinospora cordifolia* (Anuj and Ishnava, 2013), *Aloe vera* (Chandran et al., 2006), *Terminalia chebula* (Edison and Sethuraman, 2012), *Catharanthus roseus* (Mukunthan et al., 2011), *Ocimum tenuiflorum* (Patil et al., 2012), *Azadirachta indica* (Tripathi et al., 2009), *Emblica officinalis* (Ankamwar et al., 2005), *Cocos nucifera* (Roopan et al., 2013) and some common spices like *Piper nigrum* (Shukla et al., 2010) and *Cinnamom zeylicum* (Satishkumar et al., 2009). Plant extracts are known to act as reducing and stabilizing agents in the synthesis of metal nanoparticles. Metabolites, proteins and chlorophyll present in the plant extracts were found to be efficient in controlling the growth and morphology of the metal nanoparticles (Sista et al., 2016; Mondal et al., 2014).

In the present study, we are interested in using the

extract of *Kigelia africana* fruits, both as a reducing and stabilizing agents in the synthesis of monometallic silver and copper-silver bimetallic nanoparticles. *K. africana* (syn. *Kigelia pinnata*, *Kigelia aethiopica*) is a tropical plant that belongs to the Bignoniaceae family. It is widely distributed in the South, Central and West Africa with different local names: Ketete (Bette people of Obudu, Nigeria), Ntabinim (Ibibio, Nigeria), Rawuya (Hausa, Nigeria); Uturubein (Igbo, Nigeria); Pandoro, Iyan (Yoruba, Nigeria); Bechi (Nupe, Nigeria); Mwegea (Swahili, Kenya, Tanzania); Umfongothi (Zulu, South Africa) (Mann et al., 2003; Otimenyin and Uzochukwu, 2012). In Hindi (India) it is known as Balmkheera (Saini et al., 2009). The plant is commonly called Cucumber-like or Sausage tree, and different parts (leaves, bark and fruits) have found therapeutic uses traditionally in the treatment of different ailments such as gonorrhoea, sphyllis, jaundice, madness, cataract, blood cleanser, high blood pressure, hydrocephalus, measles, hemorrhagia and postpartum bleeding, ulcer etc. (Olatunji and Atolani, 2009; Grace et al., 2002; Abdulkadir et al., 2015, Kamau et al., 2016; Atawodi and Olowoniyi, 2015). Various chemical investigations have been carried out on *K. africana* and many chemical compounds mainly iridoids, naphthaquinones, monoterpenoidnaphthaquinones, isocoumarins, caffeic acid, norviburtinal, lignans, sterols and flavonoids have been identified (Gabriel and Olubunmi, 2009). Chemical analysis of the polar extract of fruit indicated the presence of vermonosides (Picerno et al., 2005), phenylpropanoid derivative identified as 6-p-coumaroyl-sucrose, and flavonoid glycoside (Gouda et al., 2006). Herein, we report the green synthesis and antimicrobial studies of silver nanoparticles (AgNPs) along with the bimetallic copper-silver nanoparticles mediated by aqueous extract of *K. africana* fruits.


## MATERIALS AND METHODS

All the chemicals were of analytical grade and were used as purchased without further purification. *K. africana* fruits were collected from Agasham mountain in Ukwel-Obudu village of Obudu LGA of Cross River State, Nigeria.

### Preparation of plant extract

The fruits of *K. africana* weighing 50 g and 0.5 m long (Figure 1a) were washed thoroughly with distilled water, cut into small sizes (with their seeds carefully selected out) and blended together in 100 cm<sup>3</sup> distilled water using a manual blender. The resultant mixture was filtered and the filtrate stored at 4°C.

\*Correspondence author. E-mail: ayiayi72@gmail.com. Tel: +2348035961521.

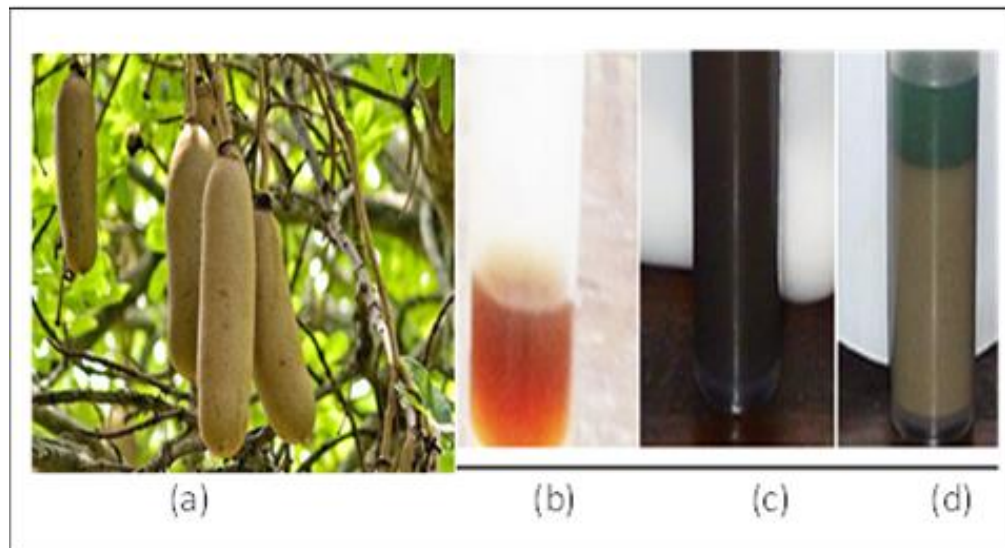

**Figure 1.** (a) *Kigelia africana* plant showing the fruits used in the present study; (b) Aqueous extract of *Kigelia africana* fruits; (c) AgNPs; (d) AgCuCl bimetallic nanoparticles synthesized by the extract.

### Synthesis of the nanoparticles

In this ecofriendly synthetic method, the procedure adopted used silver nitrate ( $\text{AgNO}_3$ ), copper chloride ( $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$ ) and aqueous extract of *K. africana* fruit. In a typical synthesis of silver nanoparticles (AgNPs),  $\text{AgNO}_3$  (1.0 g,  $5.83 \times 10^{-06}$  mM) was dispersed in  $10 \text{ cm}^3$  of aqueous extract of *K. africana* fruit under continuous stirring resulting in a brownish colouration, indicative of  $\text{Ag}^+$  reduction. The reaction mixture was then heated at  $120^\circ\text{C}$  under reflux. Six portions of  $1 \text{ cm}^3$  of the mixture was taken out from the reaction vessel after every 1 h, the reaction was stopped after 6 h. A colour change from coffee brown to dark suspension with a yellow supernatant was observed. The products were centrifuged at 3000 rpm for 15 min, filtered and washed with distilled water, dried at room temperature and stored in airtight container for further analysis. In synthesizing AgCuCl bimetallic nanoparticles, silver and copper salts were mixed together in the ratio of 1: 2. In a typical reaction,  $\text{AgNO}_3$  (2.0 g,  $1.17 \times 10^{-05}$  mM) was dispersed in  $6 \text{ cm}^3$  of aqueous extract of *K. africana*, followed by  $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$  (2.0 g,  $2.34 \times 10^{-05}$  mM) under magnetic stirring with the formation of a black homogenous colloidal dispersion. When the reaction mixture was subjected to heat treatment at  $120^\circ\text{C}$  under reflux, a colour change from black to green was observed, indicative of oxidation.

### Characterization

The bioreductions were monitored using UV-visible spectrophotometer (Evolution 201 spectrophotometer) at regular interval with samples dissolved in ethanol using quartz cuvette operated with a resolution of 1 nm. The active components in the extract responsible for the reduction were analyzed using FTIR Spectrophotometer (Shimadzu IR Affinity-1S) in the spectral range of  $4000$  to  $500 \text{ cm}^{-1}$  using KBr pellets. Scanning electron microscopy (SEM) was performed on a Hitachi S-4800 microscope attached with EDX at a voltage of 15 Kv. The sizes of the nanoparticles were determined with the help of transmission electron microscopy (TEM) measurements JEOL, TEM 1010 at 200 kV. The powder X-ray


diffraction patterns were recorded on a Bruker D8 Advanced X-ray diffractometer with Cu-K $\alpha$  radiation, having  $2\theta$  scale between 5 and  $90^\circ$ . Data intensity were collected and recorded by counting method (step: 0.014, and time; 189.5 s).

### Antimicrobial studies

Antimicrobial susceptibility test was done in the bacteriology lab of the General Hospital Calabar, Cross River State. The agar diffusion test (disc diffusion method) was adopted (Prescott et al., 2005). Muller-Hilton agar was prepared from a dehydrated base according to the manufacturer's instruction. The medium was allowed to cool to  $47^\circ\text{C}$  and poured into petri-dishes that were arranged and labeled according to their microbial isolates, and allowed to set on a level surface to a depth of approximately 4 mm. When the agar had solidified, the plates were dried for 20 min at  $35^\circ\text{C}$  by placing them in an upright position in hot air oven with the lids tilted. A discrete colony of each of the isolate was picked with a sterile wire loop and streaked on the Muller-Hilton agar according to their names as labeled: *staphylococcus aureus*, *Pseudomonas aeruginosa*, *Escherichia coli*, *Klebseilla pneumonia* (bacteria) and *Candida albicans* (fungus). Filter paper discs carrying 2000  $\mu\text{g/ml}$  AgNPs, CuAgNPs, plant extract and antibiotics; Ciprofloxacin (10  $\mu\text{g}$ ), Ofloxacin (30  $\mu\text{g}$ ), Augmentin (25  $\mu\text{g}$ ), Ceftriaxone (25  $\mu\text{g}$ ), Meropenem (30  $\mu\text{g}$ ) and Racinef (30  $\mu\text{g}$ ) were transferred to the appropriate locations on the agar plates with the help of sterile forceps. The plates were then incubated at  $37^\circ\text{C}$  for 18 h. At the end of the incubation, the zones of inhibition or no inhibition (for resistant strains) were measured and recorded in millimeters.

## RESULTS AND DISCUSSION

Silver nanoparticles (AgNPs) and copper-silver bimetallic nanoparticles (AgCuNPs) were synthesized via green synthetic route by reduction of the metal ions with aqueous

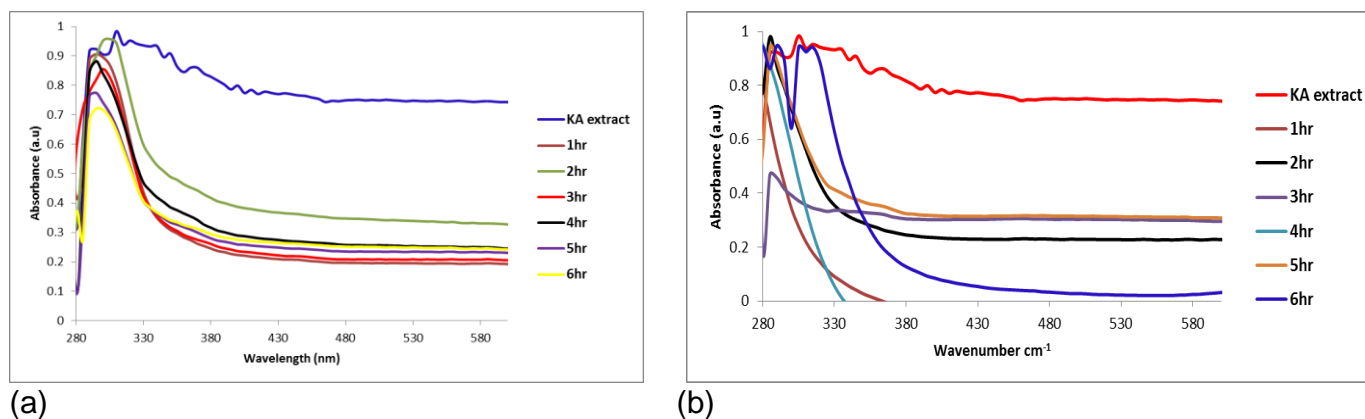

**Figure 2.** UV-Vis spectra of synthesized particles from *Kigelia africana* fruit extract at different heating time intervals: a) AgNPs b) Cu-AgNPs.


extract of *Kigelia africana* fruit. The main goal of the study is an evaluation of the potential of the plant extract as a reducing agent, which can replace the chemical reducing agents that are toxic to the environments. The bioreduction of the metal ions to nanoparticles was accompanied by colour change, which was monitored with the help of UV-Vis spectroscopic technique. Figure 1(b, c and d) shows the photographs of samples of aqueous extract of *k. africana* fruit, the AgNPs and AgCuNPs. The dark brownish colouration confirms the reduction of  $\text{Ag}^+$  ions to  $\text{Ag}^0$  and in the case of bimetallic mixture, gray precipitates with dark greenish colouration at the top was observed. In order to study the effect of temperature and heating time on the colloidal dispersion of the nanoparticles, some portions were taken for UV-Vis spectroscopic analyses.

In Figure 2, the UV-Vis spectra of the particles synthesized in aqueous plant extract are presented for both the AgNPs (Figure 2a) and AgCuNPs (Figure 2b). The spectra shows absorption maxima in the range of 285 to 350 nm for 1 to 6 h of heating, which shifts to higher wavelength with reduced intensity as the heating time increases. In literature, the surface plasmon resonance arising from the interactions of the electron cloud on the particles' surface and the electromagnetic radiation is in the range of 380 to 480 nm (Elumalai et al., 2014; Mukherjee et al., 2008; Kahrilas et al., 2014; Okafor et al., 2013; Fourough and Farhadi, 2010; Dare et al., 2014). The absorption bands in the range 285 to 350 nm observed in the present study is a clear indication of sufficient amount of reductive biomolecules in the *K. africana* fruit extract. This represents a discrete nucleation event with molecules of the active components of the extract being adsorbed on the surface of the nanoparticles. The nucleation is followed by slower controlled growth, which on heating, the particles acquired enough surface energy that promotes dissolution and second growth phase (Ostwald ripening)


with the formation of uniform mono- dispersed particles. Thus there is rapid reduction, nucleation and growth with the formation of smaller particles which are stabilized throughout the reaction period. The increased temperature resulted in increased rate of synthesis and also promoted the synthesis of smaller size particles (Fayaz et al., 2009; Kim et al., 2011; Li et al., 2011; Elemike et al., 2014; El-Rafie et al., 2011).

The phytochemical screening reported on the aqueous extract of the plant revealed the presence of some phenolic compounds, alkaloids, and flavonoids (Gabriel and Olubunmi, 2009; Picerno et al., 2005; Gouda et al., 2006; Mobark et al., 2015). The anions of these compounds interact and are adsorbed on the surface of the nanoparticles, thus stabilizing the particles formed. To ascertain these interactions, FTIR spectroscopic measurements were carried out on the synthesized nanoparticles.

Figure 3 gives the FTIR spectra of the AgNPs and Ag-Cu bimetallic nanoparticles grown in the plant extract. The infrared spectra shows common absorption bands in the samples isolated even after centrifugation and washing, indicative of the adsorption of the secondary metabolites on the surface of the particles. A broad intense band at  $3444\text{ cm}^{-1}$  in the spectrum of AgNPs can be attributed to the N-H stretching vibration arising from the peptide linkages present in the proteins of the extract (Mondal et al., 2014; Anuj and Ishnava, 2013; Mubayi et al., 2012). This broad band in the case of Ag-CuNPs, split into shoulders at  $3427$ ,  $3502$  and  $3564\text{ cm}^{-1}$  which can be assigned to the overtone of the amide-II band and the stretching vibration of the O-H group, possibly arising from the carbohydrates and/or proteins present in the sample. The absorption band at  $1622\text{ cm}^{-1}$  for AgNPs and  $1625\text{ cm}^{-1}$  for Ag-CuNPs are due to amide-I bond of proteins, indicating predominant surface capping species having C=O functionality which are mainly responsible for

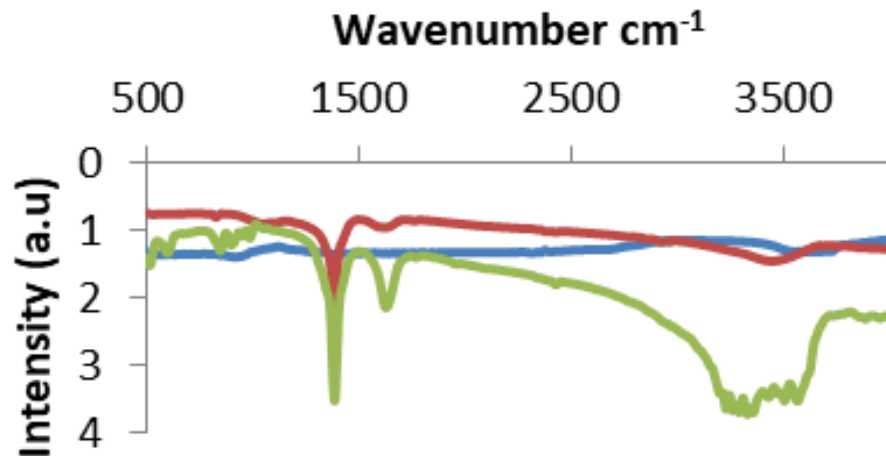

**Figure 3.** FTIR spectra of aqueous extract of *Kigelia africana* (blue), AgNPs (red) AgCu NPs (green).

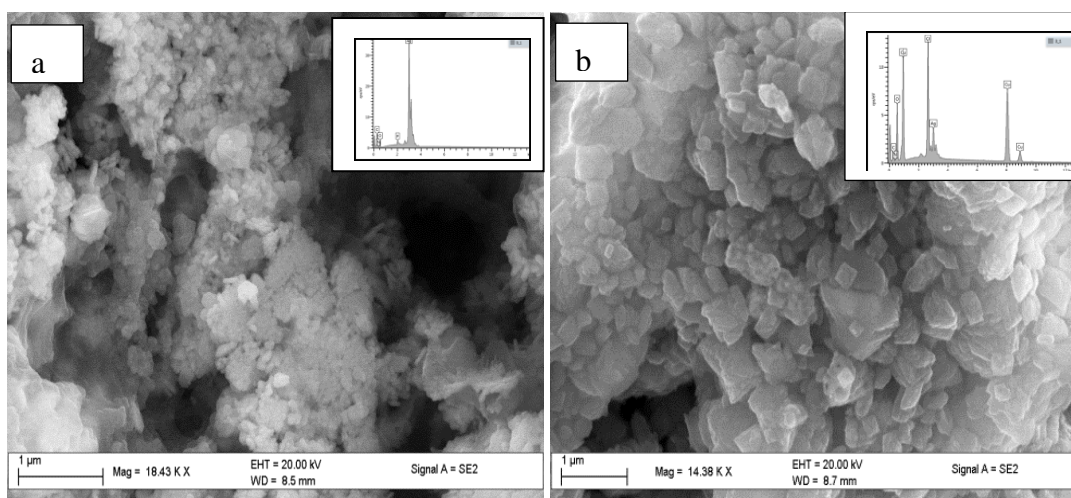

**Figure 4.** Representative SEM image (a) AgNPs (inset EDX spectrum) b) AgCuNPs (inset EDX spectrum) synthesized from the extract of *Kigelia africana* fruits.

stabilization (Mubayi et al., 2012; Mukherjee et al., 2008). The bands between  $3016$  and  $2349\text{ cm}^{-1}$  can be assigned to C–H stretching and in-plane vibrations of the phenolic ring of plants metabolites. The band at  $\sim 1045\text{ cm}^{-1}$  largely might be due to the -C-O- groups of the polyols viz. flavones, terpenoids and the polysaccharides present. The band at  $1382\text{ cm}^{-1}$  is attributed to the  $\nu(\text{C-N})$  stretching vibration present in both AgNPs and Ag-CuNPs. The various assignments are in agreement with similar compounds reported in literature.

The representative scanning electron micrographs of the AgNPs and Ag-CuNPs synthesized in the extract are, respectively shown in Figure 4a and b. The AgNPs

consists of monodisperse microspheres, while the Cu-Ag consists of anisotropic microplates. The energy dispersive X-ray (EDX) overall scans of both mono (inset of Figure 4a) and bimetallic nanostructures (inset of Figure 4b) showed the presence of carbon, nitrogen, oxygen and phosphorus originating from the secondary metabolites in the plant extracts, which acts as stabilizers. The peak around  $3.0\text{ keV}$  correspond to the binding energies of AgNPs. This peak is reduced in intensity in the case of bimetallic particles with additional copper peak at about  $8.0\text{ keV}$ . The weight percent of Ag is  $80.64$  and  $8.69$ , respectively, for AgNPs and AgCuNPs.

Figure 5 shows the representative TEM micrograph of

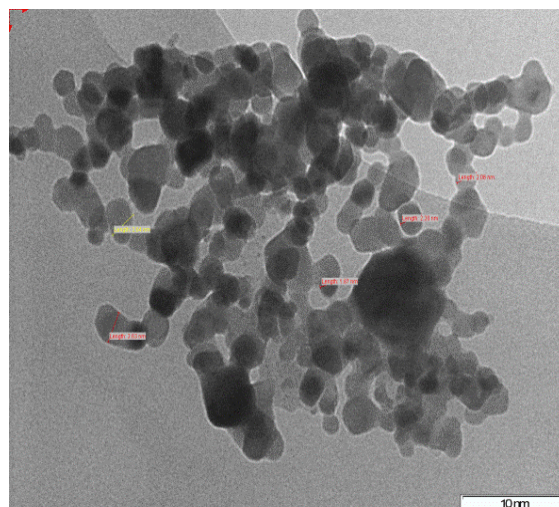


Figure 5. TEM micrograph of Cu-AgNPs


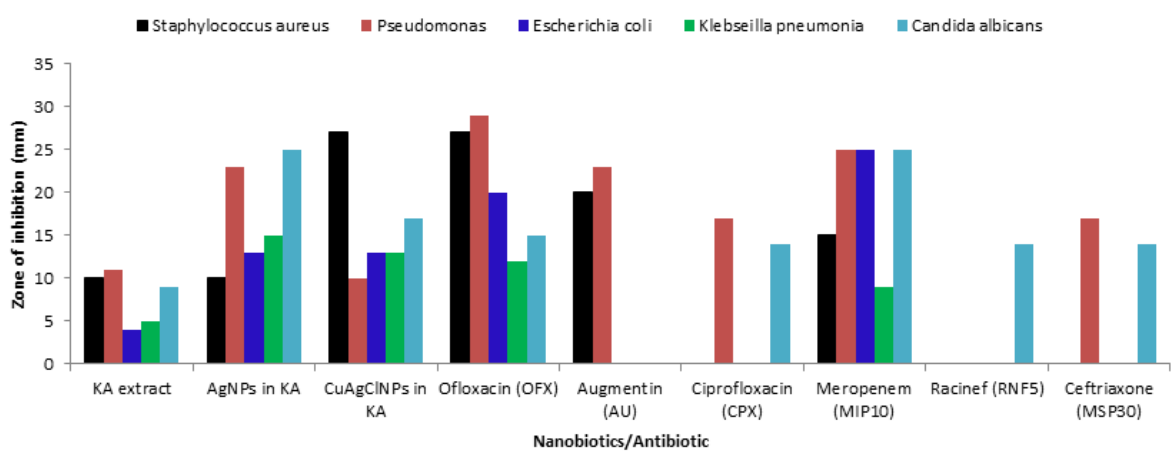


Figure 6. Antimicrobial activities of green synthesized nanoparticles using aqueous extract of *Kigelia africana* fruit.

the copper-silver nanoparticles. The particles are in the size range of 10 nm. Antimicrobial activities of the synthesized AgNPs and AgCuNPs were evaluated by using standard assay. The nanoparticles showed inhibition zone against all the bacteria (*K. pneumoniae*, *E. Coli*, *S. aureus* and *P. aeruginosa*) and fungus (*C. albicans*) under study as presented in Figures 6 and 7. The zone of inhibition of AgNPs obtained against *C. albicans* and *P. aeruginosa* are 25 and 23 mm, respectively, and are found to be higher than those of AgCuNPs. Whereas ZOI of AgCuNPs for *S. aureus* is 27 mm compared with 10 mm of AgNPs. This is indicative of the fact that the antibacterial sensitivity of the gram-positive *S. aureus* is lower for AgNPs as previously reported (Anuj and Ishnava, 2013; Sista et al., 2016;

Mukherjee et al., 2008; Kahrilas et al., 2014; Okafor et al., 2013; Forough and Farhadi, 2010; Dare et al., 2014; Elemike et al., 2014; El-Rafie et al., 2011; Fayaz et al., 2009; Kim et al., 2011; Li et al., 2011; Soo-Hwan et al., 2011), but higher for AgCu bimetallic nanoparticles.

It is interesting to note that AgCu bimetallic nanoparticles synthesized from *K. africana* are crystalline in nature and have been found to be very active in inhibiting *S. aureus*. When compared with the standard antibiotics such as ofloxacin, augmentin, ciprofloxacin, meropenem or Racinef used as control in the present study, both the AgNPs and AgCuNPs have shown higher ZOI (15 mm for AgNPs and 13 mm for AgCuNPs) against *K. pneumoniae*. This inhibitory effect is also higher than those reported by Mubayi et al. (2012). The bacterial strain

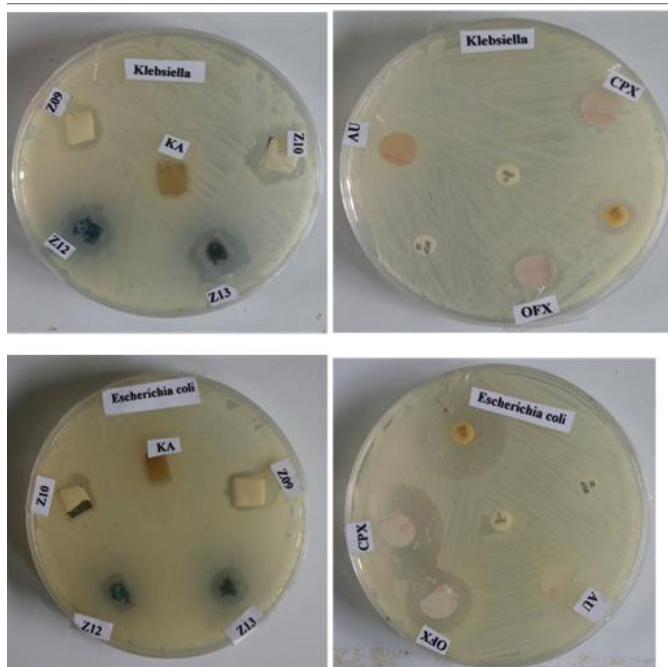

**Figure 7.** Representative plates showing zones of inhibition: Z09= AgNPs, Z13 = AgCuNPs, KA = *Kigelia africana* fruit extract, OFX = ofloxacin, CPX = ciprofloxacin, AU = augmentin.

of *E. coli* showed inhibition zone of 13 mm for both AgNPs and AgCuNPs. The nanoparticles obtained from *K. africana* fruit extract have been found to be more effective against both gram-negative and gram-positive bacterial strains.

## Conclusion

Silver nanoparticles and copper-silver bimetallic nanoparticles have been successfully synthesized using aqueous extract of *K. africana* fruits. The SEM/EDX analyses confirm that nanostructures have been synthesized, while XRD shows that the particles are crystalline in nature. TEM reveals average particle size of 10 nm. UV-Vis and FTIR spectroscopic analyses showed that molecules of the active components of the plant extract are adsorbed on the surface of the particles, thus serving as stabilizing agents. The nanoparticles inhibit the growth of both Gram-negative and Gram-positive bacteria. The present nanoparticles synthesized from aqueous extract of *K. africana* fruits inhibits *K. pneumoniae* more than any of antibiotics tested in this study. It competes very well with augmentin against *P. aeruginosa* and with meropenem against *C. albicans* with inhibition zones of 23 and 25 mm, respectively. The bimetallic nanoparticles have demonstrated effectiveness against *S. aureus* with maximum ZOI of 27 mm. These results will motivate

further investigation of the cytotoxicity of the synthesized nanoparticles on cancerous cells.

## CONFLICT OF INTERESTS

The authors have not declared any conflict of interests.

## ACKNOWLEDGEMENTS

P.B.A is grateful to PTFD for M.Sc. sponsorship. A.A.A is also grateful to the Royal Society of Chemistry for personal Research grant and The World Academy of Sciences for the Advancement of Science in developing countries (TWAS) for Research Grant No 12-169 RG/CHE/AF/AC-G -UNESCO FR: 3240271320. The authors are thankful to School of Chemistry, University of Kwazulu- Natal, Durban, South Africa for the excellence facilities

## REFERENCES

- Abdulkadir MN, Adedokun A, John E (2015). Phytochemical composition and antimicrobial evaluation of *Kigelia africana* LAM. Asian J. Plant Sci. Res. 5(1):14-17.
- Abid JP, Wark AW, Brevetm PF, Girault HH (2002). Preparation of silver nanoparticles in solution from a silver salt by laser irradiation. Chem. Commun. 0:792-793.

- Adelere IA, Lateef A (2016). A novel approach to the green synthesis of metallic nanoparticles: the use of agro-wastes, enzymes and pigments. *Nanotechnol. Rev.* 5(6):567-587.
- Alarcon EI, Udekwi K, Skog M, Pacioni NL, Stampelcoskie KG, González-Béjar M (2012). The biocompatibility and antibacterial properties of collagen-stabilized, photochemically prepared silver nanoparticles. *Biomaterials* 33(19):4947-4956.
- Ankamwar B, Damle C, Ahmad A, Sastry M (2005). Biosynthesis of gold and silver nanoparticles using *Emblica officinalis* fruit extract, their phase transfer and transmetallation in an organic solution. *J. Nano sci. Nanotechnol.* 5:1665-1671.
- Anuj SA, Ishnava KB (2013). Plant mediated synthesis of silver nanoparticles using dried stem powder of *Tinosporacordifolia*, Its antibacterial activity and its comparison with antibiotics. *Int. J. Pharm. Bio. Sci.* 4(4):849-863.
- Atawodi SE-O, Olowoniyi OD (2015). Pharmacological and Therapeutic Activities of *Kigelia africana* (Lam.) Benth. *Ann. Res. Rev. Biol.* 5(1):1-17.
- Ayi AA, Anyama CA, Khare V (2015). On the Synthesis of molybdenum nanoparticles under reducing conditions in ionic liquids. *J. Mater.* 2015:1-7.
- Ayi AA, Khare V, Strauch P, Girard J, Fromm KM, Taubert A (2010). On the chemical synthesis of titanium nanoparticles from ionic liquids. *Monatsh. Chem.* 141:1273-1278.
- Chaloupka K, Malam Y, Seifalian AM (2010). Nanosilver as a new generation of nanoparticle in biomedical applications. *Trends Biotechnol.* 28(11):580-588.
- Chandran SP, Chaudhary M, Pasricha R, Ahmad A, Sastry M (2006). Synthesis of gold nanotriangles and silver nanoparticles using *Aloe vera* plant extract. *Biotechnol. Prog.* 22:577-583.
- Chen P, Song LY, Liu YK (2007). Synthesis of silver nanoparticles by gamma-ray irradiation in acetic water solution containing chitosan. *Radiat. Phys. Chem.* 76:1165-1168.
- Dankovich TA, Gray DG (2011). Bactericidal paper impregnated with silver nanoparticles for point-of-use water treatment. *Environ. Sci. Technol.* 45(5):1992-1998.
- Dare EO, Oseghale OC, Hassan LA, Temitope AE, Elemike EE, Onwuka JC, Bamgbose JT (2014). Green synthesis and growth kinetics of nanosilver under bio-diversified plant extracts influence. *J. Nanostruct. Chem.* 5(1):85-94.
- Edison TJ, Sethuraman MG (2012). Instant green synthesis of silver nanoparticles using terminalia chebula fruit extract and evaluation of their catalytic activity on reduction of methylene blue. *Process Biochem.* 47:1351-1357.
- Elemike EE, Oseghale CO, Chuku A, Hassan LA, Owoseni MC, Mfon R, Dare EO, Temitope AE (2014). Evaluation of antibacterial activities of silver nanoparticles green-synthesized using pineapple leaf (*Ananas comosus*). *Micron* 57:1-5.
- El-Rafie MH, El-Nagger ME, Ramadan MA, Fouda MMG, Al Deyab SS, Hebeish A (2011). Environmental synthesis of silver nanoparticles using hydroxypropyl starch and their characterization. *Carbohydr. Polym.* 86:630-635.
- Elumalai EK, Kayalvizhi K, Silvan S (2014). Coconut water assisted green synthesis of silver nanoparticles. *J. Pharm. Bioallied Sci.* 6:241-245.
- Fayaz AM, Balaji K, Kalaichelvan PT, Venkatesan R (2009). Fungal based synthesis of silver nanoparticles - an effect of temperature on the size of particles. *Colloids Surf. B* 74:123-126.
- Forough M, Farhadi K (2010). Biological and green synthesis of silver nanoparticles. *Turk. J. Eng. Environ. Sci.* 34:281-287.
- Gabriel OA, Olubunmi A (2009). Comprehensive scientific demystification of *Kigelia africana*: A review. *Afr. J. Pure Appl. Chem.* 3(9):158-164.
- Gouda YG, Abdel-Baky AM, Darwish FM, Mohamed KM, Kasai R, Yamasaki K (2006). Phenylpropanoid and phenylethanoid derivatives from *Kigelia pinnata* D.C. fruits. *Nat. Prod. Res.* 20(10):935-939.
- Grace OM, Light ME, Lindsey KL, Moholland DA, Staden JV, Jager AK (2002). Antibacterial activity and isolation of antibacterial compounds from fruit of the traditional African Medicinal plant, *Kigelia africana*. *S. Afr. J. Bot.* 68:220-222.
- Kahrilas GA, Haggren W, Read RL, Wally LM, Fredrick SJ, Hiskey M, Owens JE (2014). Investigation of antibacterial activity by silver nanoparticles prepared by microwave-assisted green syntheses with soluble starch, dextrose, and arabinose. *ACS Sustain. Chem. Eng.* 2(2014):590-559.
- Kamau LN, Mbaabu PM, Mbaria JM, Gathumbi PK, Kiama SG (2016). Ethnobotanical survey and threats to medicinal plants traditionally used for the management of human diseases in Nyeri County, Kenya. *TANG* 6(3):e21.
- Khan A, El-Toni AM, Alrokayan S, Alsalmi M, Alhoshan M, Aldwayyan AS (2011a). Microwave-assisted synthesis of silver nanoparticles using poly-N Isopropyl Acrylamide/Acrylic Acid microgel particles. *Colloids Surf. A* 377:356-360.
- Khan Z, Al-Thabaiti SA, Obaid AY, Al-Youbi AO (2011b). Preparation and characterization of silver nanoparticles by chemical reduction method. *Colloids Surf. B* 82(2):513-517.
- Kim SH, Lee HS, Ryu DS, Choi SJ, Lee DS (2011). Antibacterial activity of silver nanoparticles against *Staphylococcus aureus* and *Escherichia coli* Korean. *J. Microbiol. Biotechnol.* 39:77-85.
- Lateef A, Azeez MA, Asafa TB, Yekeen TA, Akinboro A, Oladipo IC, Azeez L, Ojo SA, Gueguim-Kana EB, Beukes LS (2016a). Cocoa pod extract-mediated biosynthesis of silver nanoparticles: Its antimicrobial, antioxidant and larvicidal activities. *J. Nanostruct. Chem.* 6(2):159-169.
- Lateef A, Azeez MA, Asafa TB, Yekeen TA, Akinboro A, Oladipo IC, Ajetomobi FE, Gueguim-Kana EB, Beukes LS (2015). *Cola nitida*-mediated biogenic synthesis of silver nanoparticles using seed and seed shell extracts and evaluation of antibacterial activities. *BioNanoScience* 5(4):196-205.
- Lateef A, Azeez MA, Asafa TB, Yekeen TA, Akinboro A, Oladipo IC, Azeez L, Ajibade SE, Ojo SA, Gueguim-Kana EB, Beukes LS (2016b). Biogenic synthesis of silver nanoparticles using a pod extract of *Cola nitida*: Antibacterial, antioxidant activities and application as a paint additive. *J. Taibah Univ. Sci.* 10(4):551-562.
- Lateef A, Ojo SA, Oladejo SM (2016c). Anti-candida, anti-coagulant and thrombolytic activities of biosynthesized silver nanoparticles using cell-free extract of *Bacillus safensis* LAU 13. *Process Biochem.* 51(10):1406-1412.
- Li WR, Xie XB, Shi QS, Duan SS, Ouyang YS, Chen YB (2011). Antibacterial effect of silver nanoparticles on *Staphylococcus aureus*. *Biometals* 24(1):135-141.
- Mann A, Gbate M, Umar AN (2003). *Medicinal and Economic Plants of Nupeland*, JubeEvans Books & Publications, Bida. 1st Edition, 277.
- Mobark R, Mohammed O, Tajelseir K, Mustafa O (2015). Phytochemical investigation of antimicrobial activities leaves extract of *Kigelia africana*. *Biol. Chem. Res.* 3:44-50.
- Mondal NK, Chaudhury A, Mukhopadhyaya P, Chatterjee S, Das K, Datta JK (2014). Green synthesis of silver nanoparticles and its application for mosquito control. *Asian Pac. J. Trop. Dis.* 4:204-210.
- Mubayi A, Chatterji S, Rai PM, Watal G (2012). Evidence based green synthesis of nanoparticles. *Adv. Mat. Lett.* 3(6):519-525.
- Mukherjee P, Roy M, Mandal BP, Dey GK, Mukherjee PK, Ghatak J, Tyagi AK, Kale SP (2008). Green synthesis of highly stabilized nanocrystalline silver particles by a non-pathogenic and agriculturally important fungus *T. asperellum*. *Nanotechnology* 19(7).
- Mukunthan KS, Elumalai EK, Patel EN, Murty VR (2011). *Catharanthus roseus*: A natural source for synthesis of silver nanoparticles. *Asian Pac. J. Trop. Biomed.* 1(4):270-274.
- Nair R, Varghese SH, Nair BG, Maekawa T, Yoshida Y, Sakthi KD (2010). Nanoparticulate material delivery to plants. *Plant Sci.* 179:154-163.
- Okafor F, Janan A, Kukhtareva T, Edwards V, Michael CM (2013). Green synthesis of silver nanoparticles, their characterization, application and antibacterial activity. *Int. J. Environ. Res. Public Health* 10:5221-5238.
- Olatunji A, Atolani O (2009). Comprehensive scientific demystification of *Kigelia africana*: A review. *Afr. J. Pure Appl. Chem.* 3(9):159-164.
- Otimenyin SO, Uzochukwu DC (2012). Spasmolytic and Anti-diarrhea effects of the bark of *Erythrina senegalensis* and root of *Kigelia africana*. *Asian J. Pharm. Clin. Res.* 3(4):11-14.
- Pandey S, Goswami GK, Nanda KK (2012). Green synthesis of



- biopolymer-silver nanoparticle nanocomposite: An optical sensor for ammonia detection. *Int. J. Biol. Macromol.* 51:583-589.
- Pandey S, Goswami GK, Nanda KK (2013a). Nanocomposite based flexible ultrasensitive resistive gas sensor for chemical reactions studies. *Sci. Rep.* 3:2082.
- Pandey S, Goswami GK, Nanda KK (2013b). Green synthesis of polysaccharide/gold nanoparticle nanocomposite: An efficient ammonia sensor. *Carbohydr. Polym.* 94:229-234.
- Park K, Seo D, Lee J (2008). Conductivity of silver paste prepared from nanoparticles. *Colloids Surf. A* 313:351.
- Patil RS, Kokate MR, Kolekar SS (2012). Bioinspired synthesis of highly stabilized silver nanoparticles using *Ocimum tenuiflorum* leaf extract and their antibacterial activity. *Spectrochimica Acta* 91:234-238.
- Picerno P, Autore G, Marzocco S, Meloni M, Sanogo R, Aquino RP (2005). Anti-inflammatory activity of verminoside from *Kigelia africana* and evaluation of cutaneous irritation in cell cultures and reconstituted human epidermis. *J. Nat. Prod.* 68(11):1610-1614.
- Prathna TC, Chandrasekaran N, Raichur AM, Mukherjee A (2011). Biomimetic synthesis of silver nanoparticles by *Citrus limon* (lemon) aqueous extract and theoretical prediction of particle size. *Colloids Surf. B* 82(1):152-159.
- Prescott LM, Harley JP, Klein DA (2005). *Microbiology* (6<sup>th</sup> edition). McGraw-Hill, Boston.
- Prow TW, Grice JE, Lin LL, Faye R, Butler M, Becker W, Wurm EMT, Yoong C, Robertson TA, Soyer HP, Roberts MS (2011). Nanoparticles and microparticles for skin drug delivery. *Adv. Drug Delivery Rev.* 63(6):470-491.
- Reicha FM, Sarhan A, Abdel-Hamid MI, El-Sherbiny IM (2012). Preparation of silver nanoparticles in the presence of Chitosan by electrochemical method. *Carbohydr. Polym.* 89(1):236-244.
- Roopan SM, Rohit MG, Rahuman AA, Kamraj C, Bharathi A, Surendra TV (2013). Low-cost and eco-friendly phyto-synthesis of silver nanoparticles using *Coos nucifera* Coir extract and its larvicidal activity. *Ind. Crops Prod.* 43:631-635.
- Saini S, Kaur H, Verma B, Ripudaman, Singh S (2009). *Kigelia africana* (Lam.) Benth. An overview. *Nat. Prod. Rad.* 8(2):190-197.
- Sathishkumar M, Sneha K, Won SW, Cho CW, Kim S, Yun YS (2009). Cinnamon zeylanicum bark extract and powder mediated green synthesis of nano-crystalline silver particles and its bactericidal activity. *Colloids Surf. B* 73(2):332-338.
- Sathishkumar M, Sneha K, Won SW, Cho CW, Kim S, Yun YS (2009). Cinnamon zeylanicum bark extract and powder mediated green synthesis of nano-crystalline silver particles and its antibacterial activity. *Colloids Surf. A* 73:332-338.
- Shukla VK, Singh RP, Pandey AC (2010). Black pepper assisted biomimetic synthesis of silver nanoparticles. *J. Alloys Compd.* 507:13-16.
- Sista KS, Deen DG, Dan BP, Pradeep KM, Siddh NU (2016). Green synthesis of silver nanoparticles: a review. *Green Sustain. Chem.* 6:34-56.
- Sivarraman SK, Elango I, Kumar S, Santhanam V (2009). A green protocol for room temperature synthesis of silver nanoparticles in seconds. *Curr. Sci.* 97(7):1055-1059.
- Soo-Hwan J, Jung WL, Dengteng G, Kai S, Takuya N, Seong II Y, Ashish A, Yao L, Kotov NA (2011). Reversible nanoparticle gels with colour switching. *J. Mater. Chem.* 21:11639-11643.
- Tran QH, Nguyen VQ, Le A-T (2013). Silver nanoparticles: synthesis, properties, toxicology, applications and perspectives. *Adv. Nat. Sci. Nanosci. Nanotechnol.* 4:033001.
- Tripathi A, Chandrasekaran N, Raichur AM, Mukherjee A (2009). Antibacterial applications of silver nanoparticles synthesized by aqueous extract of *Azadirachta indica* (Neem) leaves. *J. Biomed. Nanotechnol.* 5:93-98.
- Vijaykumar PPN, Pammi SVN, Kollu P, Satyanarayana KVV, Shameem U (2014). Green synthesis and characterization of silver nanoparticles using *boerhaaviadiffusa* plant extract and their antibacterial activity. *Ind. Crops Prod.* 52:562-566.
- Yang J, Pan J (2012). Hydrothermal synthesis of silver nanoparticles by sodium alginate and their applications in surface-enhanced raman scattering and catalysis. *Acta Mater.* 60(12):4753-4758.
- Zhang WZ, Qiao XL, Chen JG (2006). Synthesis and Characterization of silver nanoparticles in AOT Micro-Emulsion system. *Chem. Phys.* 300:495-500.